

Topological defects in triplet superconductors UPt_3 , Sr_2RuO_4 , etc.

K. Maki,¹ S. Haas,¹ D. Parker,¹ and H. Won²

¹*Department of Physics and Astronomy, University of Southern California, Los Angeles, CA 90089-0484 USA*

²*Department of Physics, Hallym University, Chuncheon 200-702, South Korea*

After a brief introduction on nodal superconductors, we review the topological defects in triplet superconductors such as UPt_3 , Sr_2RuO_4 , etc. This is in part motivated by the surprising discovery of Ana Celia Mota and her colleagues that in some triplet superconductors the flux motion is completely impeded (the ideal pinning). Among topological defects the most prominent is Abrikosov's vortex with quantum flux $\phi_0 = \frac{hc}{2e}$. Abrikosov's vortex is universal and ubiquitous and seen in both conventional and unconventional superconductors by the Bitter decoration technique, small angle neutron scattering (SANS), scanning tunneling microscopy (STM), micromagnetometer and more recently by Lorentz electron micrograph. In order to interpret the experiment by Mota et al a variety of textures are proposed. In particular, in analogy to superfluid $^3\text{He-A}$ the $\hat{\ell}$ -soliton and $\hat{d}$ -soliton play the prominent role. We review these notions and point out possible detection of these domain walls and half-quantum vortices in some triplet superconductors.

PACS numbers:

I. INTRODUCTION

We shall first survey the new world of nodal superconductors, which appeared on the scene in 1979. Indeed nodal superconductors are a child of the 21st century [1, 2, 3]. Although the presence of nodal superconductors in heavy-fermion superconductors like CeCu_2Si_2 , UPt_3 , UBe_{13} and others was found in the late eighties [1], the systematic study of the gap function $\Delta(\mathbf{k})$ began only after the discovery of the high- T_c cuprates $\text{La}_{2-x}\text{Ba}_x\text{CuO}_4$ by Bednorz and Müller [4] in 1986. The d-wave symmetry of high- T_c cuprates YBCO, Bi-2212, etc. was established circa 1994 through the elegant Josephson interferometry [5, 6] and the powerful angle resolved photoemission spectrum (ARPES) [7] among others. In 1993 Volovik [8] derived the quasiparticle density of states of the vortex state in nodal superconductors within the semiclassical approximation. The surprising $\sqrt{H}$ dependence of the specific heat has been seen in YBCO [9], LSCO [10], and Sr_2RuO_4 [11, 12]. Later Volovik's approach was extended in a variety of directions: a) the study of the thermal conductivity [13, 14]; b) for an arbitrary field direction [15]; and c) for different classes of $\Delta(\mathbf{k})$ [16]. These are summarized in Ref.[17]. Until now the powerful ARPES and Josephson interferometry have not been applied outside of high- T_c cuprate superconductors.

Since 2001 Izawa et al have determined the gap function $\Delta(\mathbf{k})$ in Sr_2RuO_4 [18], CeCoIn_5 [19], $\kappa-(\text{ET})_2\text{Cu}(\text{NCS})_2$ [20], $\text{YNi}_2\text{B}_2\text{C}$ [21], and $\text{PrOs}_4\text{Sb}_{12}$ [22, 23] via the angle-dependent magnetothermal conductivity. These $|\Delta(\mathbf{k})|$'s are shown in Figure 1. In addition, the gap function of UPt_3 was established around 1994-6 as E_{2u} through the anisotropy in the thermal conductivity [24] and the constancy of the Knight shift in NMR [25]. Somewhat surprisingly all these superconductors are nodal and their quasiparticle density of states increases linearly in $|E|$ for $|E|/\Delta \ll 1$:

$$N(E) \sim |E|/\Delta \quad (1)$$

For example, this implies that the p-wave superconductivity in Sr_2RuO_4 as proposed in Ref. 26 is not consistent with

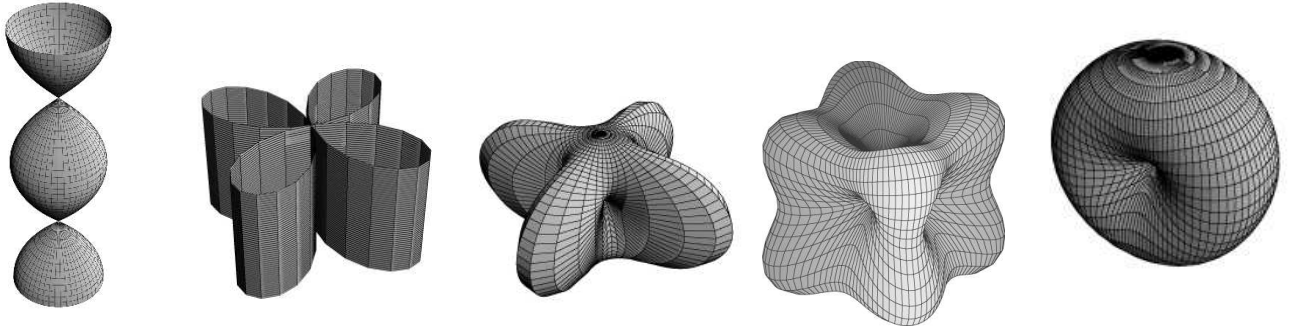


FIG. 1: From top left, order parameters for Sr_2RuO_4 , CeCoIn_5 and $\kappa-(\text{ET})_2\text{Cu}(\text{NCS})_2$, $\text{YNi}_2\text{B}_2\text{C}$, $\text{PrOs}_4\text{Sb}_{12}$ (A and B phases)

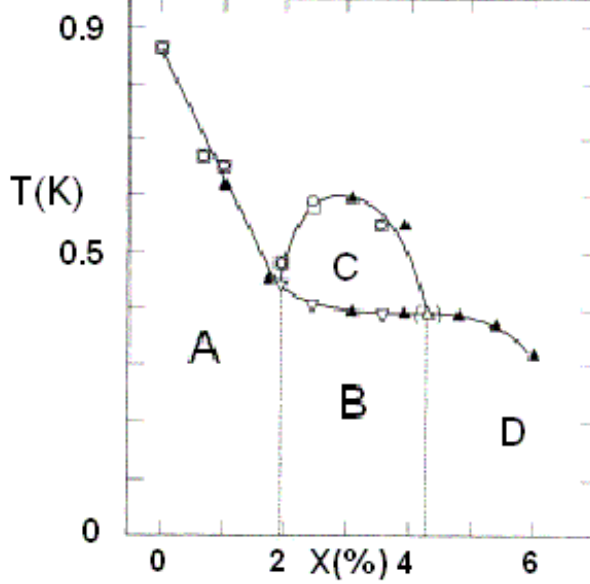


FIG. 2: Phase diagram of $U_{1-x}Th_xBe_{13}$ from Heffner et al [41].

the specific heat data [11]. Also as discussed elsewhere [27, 28], the two gap model is of little help in this matter.

More recently the quasiparticle density of states in the vortex state in Sr_2RuO_4 has been reported [29]. Indeed the observed quasiparticle density of states is very consistent with that predicted for an f-wave order parameter [30]. Also many of these superconductors are triplet: UPt_3 , Sr_2RuO_4 , $(TMTSF)_2PF_6$, $U_{1-x}Th_xBe_{13}$, URu_2Si_2 , $PrOs_4Sb_{12}$, UNi_2Al_3 and $CePt_3Si$, for example.

II. TEXTURES IN TRIPLET SUPERCONDUCTORS

Here we consider possible textures in triplet superconductors. For simplicity we concentrate on two f-wave superconductors: UPt_3 (3-dimensional) and Sr_2RuO_4 (quasi 2-dimensional), which we understand well. Mota et al [33, 34] have discovered the ideal pinning in the B phase of UPt_3 and below $T=70$ mK in Sr_2RuO_4 . Also these systems are characterized by $\hat{\ell}$ and $\hat{d}$ similarly to superfluid 3He -A [35, 36]. Here $\hat{\ell}$ is the direction of the pair angular momentum. But unlike superfluid 3He -A $\hat{\ell}$ is fixed to be parallel to one of the crystal axes: $\hat{\ell} \parallel \pm \hat{c}$. $\hat{\ell}$ can be called the chiral vector. On the other hand $\hat{d}$ describes the spin configuration of the pair and is perpendicular to the pair spin $\mathbf{S}_{pair}$. In the equilibrium configuration $\hat{d} \parallel \pm \hat{\ell}$ in superfluid 3He -A, UPt_3 and Sr_2RuO_4 [26]. Also we believe that some triplet superconductors may not have $\hat{\ell}$ and $\hat{d}$ vectors, as observed in superfluid 3He -B. So it is very important to know if the superconductivity breaks the chiral symmetry, as observed in the experiments by Mota et al [33, 34] on the B phase in $U_{1-x}Th_xBe_{13}$ (see Fig. 2). But it is possible that the superconductor in UBe_{13} does not have $\hat{\ell}$ and $\hat{d}$. Also we conjecture that the superconductivity in the B phase of $PrOs_4Sb_{12}$ has $\hat{\ell}$ and $\hat{d}$ vectors [23] and that probably all other quasi 2-dimensional systems such as URu_2Si_2 , UNi_2Al_3 and $CePt_3Si$ do as well. Therefore we can think of a variety of domain walls as in superfluid 3He -A [38, 39]. Indeed the $\hat{\ell}$ -soliton in Sr_2RuO_4 has been considered by Sigrist and Agterberg [40]. The $\hat{\ell}$ -soliton is created when in one side of the wall $\hat{\ell} \parallel \hat{c}$, while in the other side $\hat{\ell} \parallel -\hat{c}$. The chirality changes across the $\hat{\ell}$ -soliton. However, unlike in superfluid 3He -A $\hat{\ell}$ is practically fixed to be parallel to $\pm \hat{c}$. For example, when $\hat{\ell}$ is in the ab-plane there will be little superconducting order parameter left. Therefore we can estimate the $\hat{\ell}$ -soliton energy per unit area as

$$f_{\hat{\ell}} \simeq \frac{1}{4} N_0 \Delta^2(T) \xi(T) \quad (2)$$

$$\simeq \frac{1}{4} N_0 v_F \Delta(T) \quad (3)$$

where $\Delta(T)$ is the maximum value of the energy gap and v_F is the Fermi velocity.

On the other hand the $\hat{d}$ -soliton may be much more easily created [42]. The crucial element here is the spin-orbit energy which binds $\hat{d}$ parallel to $\hat{\ell}$. The relevant energy can deduced from the NMR data of UPt₃ [43] and Sr₂RuO₄ [44]. We estimate $\Omega(T)/\Delta(T)$ for UPt₃ and Sr₂RuO₄: $\Omega(T)/\Delta(T) \sim 0.5 \times 10^{-3}$ (B phase) and 0.2×10^{-4} respectively. Here $\Omega(T)$ is the characteristic frequency associated with the $\hat{\ell}$ and $\hat{d}$ coupling [42]. Then the areal energy for the $\hat{d}$ -soliton is given by

$$f_{\hat{d}} \simeq \frac{1}{4} N_0 v_F \Omega(T). \quad (4)$$

This is smaller than $f_{\hat{\ell}}$ for UPt₃ and Sr₂RuO₄ by factors of 0.5×10^{-3} and 0.2×10^{-4} , respectively. Also $\xi_d = v_F/\Omega(T)$ gives the spatial extension of the domain well. This ranges from $10\mu\text{m} \sim 1\text{ mm}$.

In the presence of $\hat{\ell}$ -solitons vortices may enter into the superconducting state as observed in the vortex sheet of superfluid ³He-A [45, 46]. Otherwise the motion of the vortex across the $\hat{\ell}$ -soliton is completely impeded as discussed in [40]. When an Abrikosov vortex encounters a $\hat{d}$ -soliton, the vortex appears to split into two half-quantum vortices (HQV) in the vicinity of $T \simeq T_c$. At lower temperatures it appears that Abrikosov's vortex should tunnel through the $\hat{d}$ -soliton. This type of HQV was first predicted in the context of superfluid ³He-A [47, 48, 49]. However, these HQV's have not yet been observed in superfluid ³He-A [50]. Therefore half-quantum vortices may be first observed in triplet superconductors.

III. HALF-QUANTUM VORTICES

Here we shall consider a pair of half-quantum vortices (HQV) attached to a $\hat{d}$ -soliton [42]. The texture free energy is given by

$$f_{pair} = \frac{1}{2} \chi_N C^2 \int dy dz (K(\nabla\phi)^2 + \sum_{i,j} |\partial_i \hat{d}_j|^2 + \xi_d^{-2} \sin^2(\Psi)) \quad (5)$$

where C is the spin wave velocity, $\xi_d = C(T)/\Omega(T)$ and

$$K = \frac{\rho_s}{\rho_{s,spin}} = \frac{1 + \frac{1}{3}F_1}{1 + \frac{1}{3}F_1^a} \frac{1 + \frac{1}{3}F_1^a(1 - \rho_s^0)}{1 + \frac{1}{3}F_1(1 - \rho_s^0)} \quad (6)$$

where ρ_s and $\rho_{s,spin}$ are the superfluid density and the spin superfluid density respectively. Here F_1 and F_1^a are the Landau parameters and $\rho_s^0(T)$ is the superfluid density when $F_1 = F_1^a = 0$. The superfluid density for UPt₃ and Sr₂RuO₄ are shown in Fig. 3. In this analysis we assumed that $|\Delta(\mathbf{k})| \sim |\cos\theta \sin^2\theta|$ and $\sim |\cos\chi|$ in UPt₃ [51] and Sr₂RuO₄ respectively. We note that ρ_s^0 in Sr₂RuO₄ is the same as in d-wave superconductivity [52]. In particular, for T in the vicinity of T_c we obtain

$$\rho_s^0 \simeq -\frac{4}{3} \ln\left(\frac{T}{T_c}\right) \text{ for Sr}_2\text{RuO}_4 \quad (7)$$

$$\simeq -\frac{143}{105} \ln\left(\frac{T}{T_c}\right) \text{ for UPt}_3 \quad (8)$$

respectively. Here we assumed that $\mathbf{H} \parallel \hat{a}$ and that the domain wall extends in the y-z plane. Here we consider 2 typical cases as shown in Fig. 4a) and b). In Fig. 4a) the $\hat{d}$ -soliton runs parallel to the c axis while in Fig. 4b) it runs parallel to the b-axis. For the first configuration (i.e. a) we parametrize $\hat{d} = \cos\psi\hat{z} + \sin\psi\hat{y}$ with

$$\psi(y, z) = \frac{1}{2} (\arctan\left(\frac{z + (R/2)}{y}\right) - \arctan\left(\frac{z - (R/2)}{y}\right)) \quad (9)$$

with 2 HQV located at $(y, z) = (0, R/2)$ and $(0, -R/2)$ while in the second configuration (b)

$$\psi(y, z) = \frac{1}{2} (\arctan\left(\frac{y + (R/2)}{z}\right) + \arctan\left(\frac{y - (R/2)}{z}\right)) \quad (10)$$

Also Φ in Eq.(7) is the phase of the order parameter $\Delta(\mathbf{k})$. Then the total free energy reduces to

$$f_{pair} = \frac{1}{2} \chi_N C^2 (\pi K \ln(\lambda/R) + \pi \ln(R/\xi) + \pi \left(\frac{R}{2\xi_d}\right)^2 \times \ln(4\xi_d/R)) \quad (11)$$

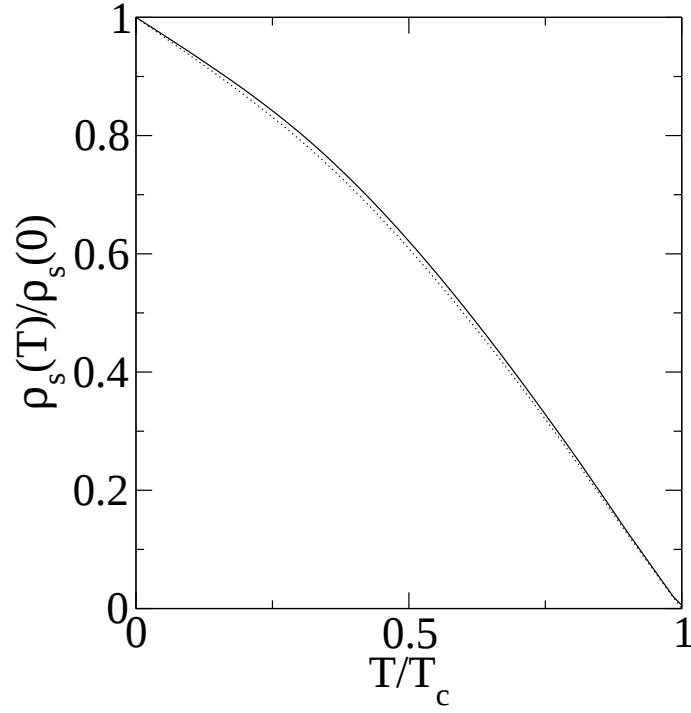


FIG. 3: The superfluid density for the B phase of UPt₃ (solid line) and Sr₂RuO₄ are shown

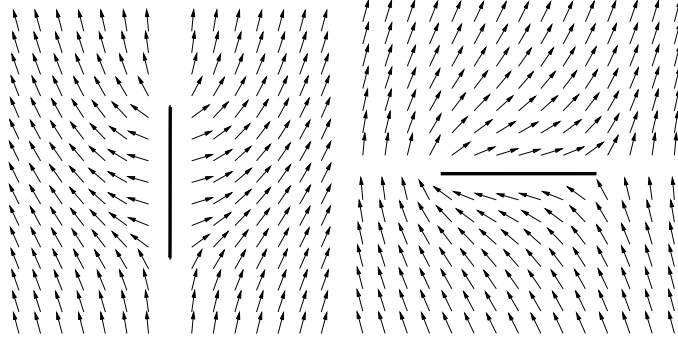


FIG. 4: The spatial orientation of the $\hat{d}$ -vector

where λ and ξ are the magnetic penetration depth and the coherence length respectively.

By minimizing f_{pair} with respect to R , we obtain

$$R_0^2 = 2\xi_d^2(K-1)/[\ln(\frac{4\xi f}{\sqrt{e}R_0})] > 0 \quad (12)$$

where R_0 is the optimal distance of a pair of HQVs. First in order to have a pair of HQVs we need $K > 1$, which is guaranteed when $F_1 > F_1^a$ and $T \simeq T_c$. Also it is necessary to have

$$R_0 < \frac{4}{\sqrt{e}}\xi_d \quad (13)$$

In particular when $K-1 \ll 1$, we obtain

$$R_0/\xi_d \simeq \frac{4}{\sqrt{e}} - \frac{\sqrt{e}}{2}(K-1) \quad (14)$$

where $e = 2.71828 \dots$. Also the separation between a pair of HQV should be of the order of $\xi_d \sim 10\mu\text{m} \sim 1\text{ mm}$.

IV. CONCLUDING REMARKS

We have described an abundance of triplet superconductors. Many of their order parameters possess the $\hat{\ell}$ and $\hat{d}$ vectors: $\Delta(\mathbf{k})$ in the B phase of UPt_3 , Sr_2RuO_4 , both the A and B phase of $\text{PrOs}_4\text{Sb}_{12}$ and perhaps many other systems. In these systems the $\hat{d}$ -soliton is the most common domain wall. The presence of the $\hat{d}$ -soliton can impede the flux motion in a variety of ways. The most intriguing is the splitting of an Abrikosov vortex into a pair of half-quantum vortices as discussed in [42]. We expect that some of the techniques used to observe Abrikosov's vortex can be used in the present circumstances. These techniques include the Bitter decoration technique [53], small angle neutron scattering (SANS) [54], scanning tunneling microscopy (STM) [55], micromagnetometer [56] and more recently Lorentz electron micrograph [57]. We expect the exploration of these topological defects in triplet superconductors will enhance our understanding of these exotic superconductors. Also they will provide ideal laboratories to check rich field-theoretical concepts at moderately low temperatures from 1 ~ 100 mK. Therefore the future of topological defects in nodal superconductors is still wide open.

Acknowledgments

We have benefitted from collaborations with Balazs Dora, Hae-Young Kee, Yong Baek Kim, András Ványolos and Attila Virosztek on related subjects.

-
- [1] M. Sigrist and K. Ueda, Rev. Mod. Phys, **63**, 239 (1991).
 - [2] H. Won, S. Haas, D. Parker, K. Maki, Phys. Stat. Sol. (6) **242**, 363 (2005).
 - [3] K. Maki, S. Haas, D. Parker, H. Won, Chinese Journal of Physics (in press).
 - [4] J.G. Bednorz and K.A. Müller, Z. Phys. B **64**, 189 (1986).
 - [5] D. J. van Harlingen, Rev. Mod. Phys. **67**, 515 (1995).
 - [6] C. C. Tsuei and J. R. Kirtley, Rev. Mod. Phys. **72**, 969 (1995).
 - [7] A. Damascelli, Z. Houssain and Z.X. Shen, Rev. Mod. Phys. **45**, 473 (2003)
 - [8] G. E. Volovik, JETP Lett. **58**, 496 (1993).
 - [9] K.A. Moler et al, Phys. Rev. Lett. **72**, 2744 (1994).
 - [10] S.J. Chen et al, Phys. Rev. B **58** 14753(R), (1998).
 - [11] S. Nishizaki, Y. Maeno and Z. Mao, J. Phys. Soc. Jpn. **69**, 573 (2000).
 - [12] H. Won and K. Maki, Europhys. Lett. **52**, 427 (2000).
 - [13] C. Kübert and J. P. Hirschfeld, Phys. Rev. Lett. **80**, 4963 (1998)
 - [14] H. Won and K. Maki, cond-mat/0004105.
 - [15] I. Vekhter, J.P. Carbotte and E.J. Nicol, Phys. Rev B **69**, 7123 (1999).
 - [16] T. Dahm, K. Maki and H. Won, cond-mat/0006307.
 - [17] H. Won, S. Haas, D. Parker, S. Telang, A. Ványolos and K. Maki, cond-mat/0501463.
 - [18] K. Izawa et al, Phys. Rev. Lett. **86**, 2653 (2001).
 - [19] K. Izawa et al, Phys. Rev. Lett. **87**, 57002 (2001).
 - [20] K. Izawa et al, Phys. Rev. Lett. **88**, 027002 (2002).
 - [21] K. Izawa et al, Phys. Rev. Lett. **89**, 137006 (2002).
 - [22] K. Izawa et al, Phys. Rev. Lett. **90**, 117001 (2003).
 - [23] K. Maki, S. Haas, D. Parker, H. Won, K. Izawa and Y. Matsuda, Europhys. Lett. **68**, 720 (2004).
 - [24] B. Lussier, B. Ellman and L. Taillefer, Phys. Rev. Lett. **23**, 3294 (1994).
 - [25] H. Tou, Y. Kitaoka, K. Asayama, N. Kimura, Y. Onuki, Y. Yamamoto and K. Maegawa, Phys. Rev. Lett. **77**, 1374 (1996).
 - [26] A.P. Mackenzie and Y. Maeno, Rev. Mod. Phys. **75**, 657 (2003).
 - [27] B. Dora, K. Maki, A. Virosztek, Europhys. Lett. **62**, 426 (2003).
 - [28] H-Y. Kee, K. Maki, C.H. Chung, Phys. Rev. B **67** 86534(R) (2003).
 - [29] C. Lupien, S.K. Dutta, B.I. Barker, Y. Maeno and J.C. Davis, cond-mat/0503317.
 - [30] M. Kato, H. Suematsu and K. Maki, Physica C **408-410**, 53 (2004).
 - [31] E. Bauer et al, Phys. Rev. Lett. **92**, 027003 (2004).
 - [32] P.A. Frigeri et al, Phys. Rev. Lett. **92**, 097001 (2004).
 - [33] A. Amann, A.C. Mota, M.B. Maple and H.v. Löhneysen, Phys. Rev. B **57**, 3640 (1998).
 - [34] E. Dumont and A.C. Mota, Phys. Rev. B **65**, 144519 (2000).
 - [35] D. Vollhardt and P. Wölfle, "The Superfluid Phases of Helium-3", (Taylor and Francis, New York, 1990).
 - [36] G.E. Volovik, "Exotic Properties of Superfluid Helium", (World Scientific Pub. Co., Singapore, 1991).
 - [37] R.H. Haffner et al, Phys. Rev. Lett. **65**, 2816 (1990).
 - [38] K. Maki and P. Kumar, Phys. Rev. B **17**, 1088 (1978).

- [39] K. Maki in “Solitons”, edited by S.E. Trullinger, V.E. Zakharov and V.L. Pokrovskii (North-Holland, Amsterdam, 1986).
- [40] M. Sigrist and D.F. Agterberg, Prog. Theor. Phys. **102**, 965 (1999).
- [41] R.H. Heffner et al, Phys. Rev. Lett. **65**, 2816 (1990).
- [42] H.-Y. Kee, Y.B. Kim and K. Maki, Phys. Rev. B **62** R 9275 (2000).
- [43] H. Tou et al, Phys. Rev. Lett. **80**, 3129 (1998).
- [44] H. Murakami et al, Phys. Rev. Lett. **93**, 167004 (2004).
- [45] M.T. Heinilä and G.E. Volovik, Physica B **210**, 300 (1995).
- [46] Ü. Parts et al, Physica B **210**, 311 (1995).
- [47] M.M. Salomaa and G.E. Volovik, Phys. Rev. Lett. **55**, 1184 (1985).
- [48] K. Maki, Phys. Rev. Lett. **56**, 1312 (1986).
- [49] C.-R. Hu and K. Maki, Phys. Rev. B **36**, 6871 (1987).
- [50] G.E. Volovik in “Vortices in Unconventional Superfluids and Superconductors”, edited by G.E. Volovik, N. Schopohl and P.R. Huebner (Springer, Berlin 2002).
- [51] G. Yang and K. Maki, Euro. Phys. J. B **21**, 61 (2001).
- [52] H. Won and K. Maki, Phys. Rev. B **49**, 1397 (1994).
- [53] P.L. Gammel, D.J. Bishop, J.P. Rice and D.M. Ginsburg, Phys. Rev. Lett. **68**, 3343 (1992).
- [54] B. Keimer et al, Phys. Rev. Lett. **73**, 3459 (1994).
- [55] I. Maggio-Aprile et al, Phys. Rev. Lett. **75**, 2764 (1995).
- [56] J.R. Kirtley et al, Appl. Phys. Lett. **66**, 1138 (1995).
- [57] A. Tonomura et al, Nature **397**, 308 (1999).